



## ISTITUTO NAZIONALE DI RICERCA METROLOGICA Repository Istituzionale

Preparation and Characterisation of PBAT-Based Biocomposite Materials Reinforced by Protein Complex Microparticles

*Original*

Preparation and Characterisation of PBAT-Based Biocomposite Materials Reinforced by Protein Complex Microparticles / Togliatti, Elena; Laporta, Cosimo C.; Grimaldi, Maria; Pitirillo, Olimpia; Cavazza, Antonella; Pugliese, Diego; Milanese, Daniel; Sciancalepore, Corrado. - 7:(2021). ( 2nd International Online Conference on Polymer Science—Polymers and Nanotechnology for Industry 4.0 Online 1-15 November 2021) [10.3390/IOCPS2021-12019].

*Availability:*

This version is available at: 11696/77386 since:

*Publisher:*

MDPI

*Published*

DOI:10.3390/IOCPS2021-12019

*Terms of use:*

This article is made available under terms and conditions as specified in the corresponding bibliographic description in the repository

*Publisher copyright*

(Article begins on next page)

# Preparation and Characterisation of PBAT-Based Biocomposite Materials Reinforced by Protein Complex Microparticles <sup>†</sup>

Elena Togliatti <sup>1,2,\*</sup> , Cosimo C. Laporta <sup>1</sup>, Maria Grimaldi <sup>3</sup> , Olimpia Pitirollo <sup>3</sup>, Antonella Cavazza <sup>3</sup> ,  
Diego Pugliese <sup>2,4</sup> , Daniel Milanese <sup>1,2</sup> and Corrado Sciancalepore <sup>1,2</sup> 

<sup>1</sup> DIA, Dipartimento di Ingegneria e Architettura, Università di Parma, Parco Area delle Scienze 181/A, 43124 Parma, Italy; cosimocataldo.laporta@studenti.unipr.it (C.C.L.); daniel.milanese@unipr.it (D.M.); corrado.sciancalepore@unipr.it (C.S.)

<sup>2</sup> INSTM, Consorzio Interuniversitario Nazionale di Scienza e Tecnologia dei Materiali, Via G. Giusti 9, 50121 Firenze, Italy; diego.pugliese@polito.it

<sup>3</sup> SCVSA, Dipartimento di Scienze Chimiche, Della Vita e della Sostenibilità Ambientale, Università di Parma, Parco Area delle Scienze 17/A, 43124 Parma, Italy; daianagrimaldi@hotmail.it (M.G.); olimpia.pitirollo@unipr.it (O.P.); antonella.cavazza@unipr.it (A.C.)

<sup>4</sup> DISAT, Dipartimento di Scienza Applicata e Tecnologia, Politecnico di Torino, Corso Duca degli Abruzzi 24, 10129 Torino, Italy

\* Correspondence: elena.togliatti@studenti.unipr.it

<sup>†</sup> Presented at the 2nd International Online Conference on Polymer Science—Polymers and Nanotechnology for Industry 4.0, 1–15 November 2021; Available online: <https://iocps2021.sciforum.net/>.

**Abstract:** In this work, new biodegradable composite materials based on poly (butylene adipate terephthalate) (PBAT) reinforced with zein–TiO<sub>2</sub> complex microparticles were prepared and characterised by electron microscopy and tensile and dynamic-mechanical tests. The composite pellets were prepared by solvent casting with different filler contents, namely 0, 5.3, 11.1 and 25 part per hundred resin (phr), to modify and modulate the properties of the final materials. Scanning electron microscopy (SEM) images showed homogeneous dispersion of the filler, without microparticles aggregation or phase separation between filler and matrix, suggesting a good interphase adhesion. According to tensile tests, Young’s modulus showed an improvement in the rigidity and the yield stress presented an increasing trend, with opposite behaviour compared to other composites. Dynamic-mechanical analysis (DMA) results exhibited increasing storage modulus values, confirming a greater rigidity with a higher filler percentage. The glass transition temperature showed a slightly increasing trend, meaning the presence of an interaction between the two phases of the composite materials. Overall, the produced PBAT composites showed similar properties to low-density polyethylene (LDPE), proving to be promising and more sustainable alternatives to traditional polymers commonly adopted in agri-food fields.

**Keywords:** biopolymers; biocomposites; poly (butylene adipate terephthalate); protein complex; characterisation



**Citation:** Togliatti, E.; Laporta, C.C.; Grimaldi, M.; Pitirollo, O.; Cavazza, A.; Pugliese, D.; Milanese, D.; Sciancalepore, C. Preparation and Characterisation of PBAT-Based Biocomposite Materials Reinforced by Protein Complex Microparticles. *Mater. Proc.* **2021**, *7*, 20. <https://doi.org/10.3390/IOCP2021-12019>

Academic Editor: Ana María Díez-Pascual

Published: 2 December 2021

**Publisher’s Note:** MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



**Copyright:** © 2021 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

## 1. Introduction

Among materials for packaging, plastics are the most widely used, thanks to their lightness, good mechanical behaviour, barrier properties and low cost, among others [1]. Amongst traditional plastics, the most employed are polypropylene (PP), high-density polyethylene (HDPE), low-density polyethylene (LDPE), polyethylene terephthalate (PET) and polystyrene (PS), which however are not eco-sustainable due to the problems related to their end-of-life disposal [2].

In the last few decades, increasing attention has been devoted to the study and employment of bioplastics in order to reduce the environmental impact and increase sustainability. Since bioplastics generally present poorer properties when compared to traditional plastics, the realisation of composite materials represents a valid way to improve and modulate

their characteristics. The major downside of biopolymers being their high cost [3], the use of natural biodegradable fillers is a possible solution to reduce the production costs and at the same time to preserve their degradability [4].

Poly (butylene adipate terephthalate) (PBAT) is a 100% biodegradable polymer produced from fossil resources [5], although recently it has been reported that its monomers can be obtained from renewable sources [6–8]. PBAT presents similar properties and processability to polyethylene (PE), especially high flexibility [9,10].

Zein is a prolamine protein which can be extracted in pure form from corn. Its use in polymers has been studied since the 20th century [11] as it is considered a safe biocompatible and biodegradable material [12]. Zein can be formed into films and displays good barrier properties, thanks to its hydrophobic nature [13]. However, protein films are usually tough and brittle and cannot be used as is, but protein in the form of particles can be used as the reinforcing phase in the realisation of composites which are based on a flexible polymer matrix [14], such as PBAT in this case.

Of late, zein has been functionalised in protein–TiO<sub>2</sub> complexes for packaging, environmental and medical applications [15].

The aim of this work was to design and fabricate biocomposites based on PBAT loaded with microparticles of a zein–TiO<sub>2</sub> complex. The so-obtained composites have been characterised in terms of their mechanical and dynamic-mechanical properties.

## 2. Materials and Methods

PBAT (MAGMa Spa) pellets were dissolved into pure chloroform. The zein–TiO<sub>2</sub> complex had been previously prepared with a composition of 50–50 wt%, by first dissolving the zein (Sigma-Aldrich, St. Louis, MO, USA) in ethanol at 50 °C and then adding TiO<sub>2</sub> (Carlo Erba, Emmendingen, Germany) under constant stirring until a homogeneous phase was obtained. After casting and ethanol evaporation, the recovered material was milled and sieved at 25 µm, and the so-obtained powder was homogeneously dispersed into the polymer solution at the concentrations of 0, 5.3, 11.1 and 25 phr. After solvent evaporation, the obtained films were used for the production of different loaded composite samples, named PBAT, PBAT + 5.3P, PBAT + 11.1P and PBAT + 25P, respectively.

Dumbbell specimens, model 1BA according to the UNI EN ISO 527 standard, of each composite were produced by injection moulding and their mechanical properties were characterised.


Uniaxial tensile test (UTT) results allowed the evaluation of the characteristic parameters, such as Young's modulus  $E$ , yield stress  $\sigma_Y$ , elongation at break  $\varepsilon_B$ , stress at break  $\sigma_B$  and toughness  $T$ .

DMA measurements were carried out according to ASTM D7028 standard with a single cantilever clamp for the determination of the storage modulus ( $E'$ ), the loss modulus ( $E''$ ) and the loss factor ( $\tan\delta$ ).

SEM images were acquired to investigate the internal microstructure of the composites, by means of a field emission gun SEM (FESEM, Nova Nano SEM 450, FEI company, Hillsboro, OR, USA). SEM was performed on the central cross-section of the specimens obtained through a cryo-fracture.

## 3. Results and Discussion

In Figure 1, SEM images at different magnifications of PBAT and PBAT + 25P are reported as representative samples. The morphology of the filler particles (as visible in detail in Figure 1d) emphasises the protein–TiO<sub>2</sub> complex nature, showing bright-white areas corresponding to the TiO<sub>2</sub> portion and a greyer part representing the zein protein.

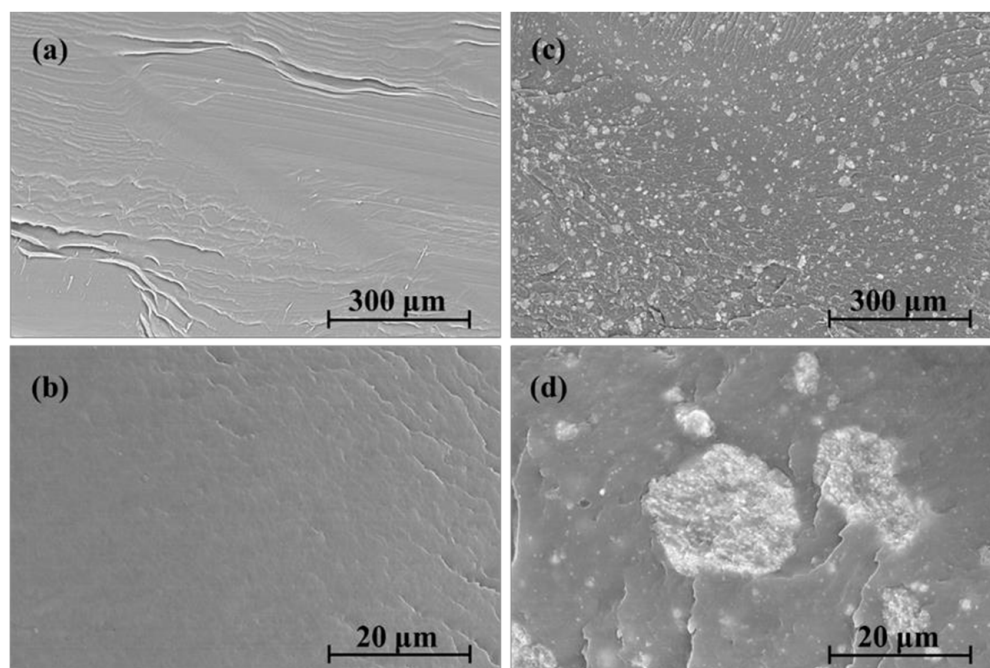

**Figure 1.** SEM images of PBAT (a,b) and PBAT + 25P (c,d) at different magnifications, as representative samples.

The images display homogeneous dispersion of the protein complex within the polymer matrix, even at a high concentration of the filler, with no aggregation of the particles and no phase separation (Figure 1b). Indeed, a region with an intermediate shade of grey is visible at the grain boundaries. This suggests the formation of an actual interfacial layer bonding the PBAT matrix to the protein due to the presence in the protein structure of both polar and non-polar functional groups [16], able to interact with the polymer macromolecules. Therefore, good adhesion and interaction between the phases can be supposed.

UTT results on the prepared biocomposites indicated a pronounced increase, up to 47%, in the  $E$  modulus with increasing filler content. An important result is the increasing trend shown by  $\sigma_Y$ , significantly different from what is traditionally displayed by other composite materials [17]. The obtained results can be interpreted as additional evidence of the good interaction between the phases involved in the biocomposite [18]. The characteristic parameters  $\epsilon_B$ ,  $\sigma_B$  and  $T$  showed a decrease with increasing filler content, related to the increased stiffening of the composites. The representative values are reported in Table 1.

**Table 1.** Young's modulus ( $E$ ), yield stress ( $\sigma_Y$ ), stress at break ( $\sigma_B$ ), elongation at break ( $\epsilon_B$ ) and toughness ( $T$ ) values of poly (butylene adipate terephthalate) (PBAT) and protein complex composites.

| Sample       | $E$ (MPa) | $\sigma_Y$ (MPa) | $\sigma_B$ (MPa) | $\epsilon_B$ (MPa) | $T$ (MJ/m <sup>3</sup> ) |
|--------------|-----------|------------------|------------------|--------------------|--------------------------|
| PBAT         | 126 ± 12  | 8.1 ± 0.2        | 13 ± 1           | 4.0 ± 0.8          | 45 ± 6                   |
| PBAT + 5.3P  | 131 ± 10  | 8.4 ± 0.2        | 12 ± 1           | 3.7 ± 0.3          | 35 ± 4                   |
| PBAT + 11.1P | 149 ± 4   | 8.8 ± 0.2        | 11 ± 1           | 3.5 ± 0.2          | 32 ± 3                   |
| PBAT + 25P   | 186 ± 11  | 8.9 ± 0.1        | 9 ± 1            | 2.7 ± 0.2          | 22 ± 2                   |

The  $E'$  modulus obtained from DMA analysis as a function of the temperature exhibited a linear increase with increasing filler content in the composite, thus confirming the stiffening effect obtained by the addition of high amounts of filler (Figure 1c).

Other authors have investigated similar biocomposite systems, based on biopolymers reinforced with natural filler particles at different concentrations [19], finding a similar

increasing behaviour of  $E'$  compared to the system studied in the present work. The enhanced modulus in composite materials can be attributed to the restricted mobility of the polymer chains due to the physical presence of the filler particles and to the chemical interaction at the interface between the polymer and the particles [20].

The glass transition temperature ( $T_g$ ) was calculated as the temperature corresponding to the peak of the  $\tan\delta$  curves, defined by the ratio between  $E''$  and  $E'$  moduli. The values of  $T_g$  for the different composites show a slight increase as the filler content increases, confirming the interaction between matrix and filler, as observed in other composite systems [21]. Table 2 displays the discussed results of DMA tests.

**Table 2.** DMA representative results of PBAT and protein complex composites.

| Sample      | $E' @ 0^\circ\text{C}$ (MPa) | $E' @ 20^\circ\text{C}$ (MPa) | $E' @ 40^\circ\text{C}$ (MPa) | $T_g$ ( $^\circ\text{C}$ ) |
|-------------|------------------------------|-------------------------------|-------------------------------|----------------------------|
| PBAT        | $273 \pm 60$                 | $202 \pm 50$                  | $155 \pm 50$                  | $-20.4 \pm 0.9$            |
| PBAT + 5.3P | $297 \pm 60$                 | $224 \pm 70$                  | $182 \pm 60$                  | $-20.3 \pm 0.8$            |
| PBAT + 11P  | $319 \pm 70$                 | $239 \pm 60$                  | $192 \pm 70$                  | $-18.3 \pm 0.5$            |
| PBAT + 25P  | $395 \pm 50$                 | $294 \pm 50$                  | $235 \pm 60$                  | $-17.9 \pm 0.5$            |

#### 4. Conclusions

Among the different biopolymers, PBAT is one of the most studied and promising biodegradable plastic materials. In this work, it was employed in the fabrication of biocomposites reinforced with a zein–TiO<sub>2</sub> complex at different concentration. The addition of different amounts of filler enabled modulation of the material properties.

The filler particles were homogeneously dispersed, as emerged from SEM images of the analysed samples, and with the presence of an interface connecting layer between the protein complex and the polymer matrix. The protein complex appeared to have a stiffening effect on the polymer matrix, with an increase of the  $E$  and  $\sigma_Y$ , suggesting, therefore, an effective good interfacial interaction between the phases.

The stiffening effect was confirmed by the increasing trend observed in the  $E'$  modulus calculated from DMA analysis. Moreover,  $T_g$  values increased with increasing filler content, validating the hypothesis of an interface layer bonding the matrix and the reinforcing particles.

According to the obtained results, the biocomposites can be considered as a valid and more sustainable alternative to the non-biodegradable, fossil-based plastics generally used in the packaging field, such as LDPE.

**Author Contributions:** Conceptualisation, C.S.; methodology, C.S.; formal analysis, C.C.L.; investigation, E.T., C.C.L., M.G., O.P. and D.P.; resources, A.C.; data curation, C.C.L.; writing—original draft preparation, E.T.; writing—review and editing, D.M. and C.S.; supervision, D.M. and C.S. All authors have read and agreed to the published version of the manuscript.

**Funding:** This research received no external funding.

**Data Availability Statement:** Not applicable.

**Conflicts of Interest:** The authors declare no conflict of interest.

#### References

1. Piergiovanni, L.; Limbo, S. Food packaging. In *Materiali, Tecnologie e Qualità Degli Alimenti*, 1st ed.; Springer: Berlin, Germany, 2010; pp. 1–576.
2. Andrady, A.L.; Neal, M.A. Applications and societal benefits of plastics. *Philos. Trans. R. Soc. London, Ser. B* **2009**, *364*, 1977–1984. [[CrossRef](#)] [[PubMed](#)]
3. Harrison, J.P.; Boardman, C.; O'Callaghan, K.; Delort, A.-M.; Song, J. Biodegradability standards for carrier bags and plastic films in aquatic environments: A critical review. *R. Soc. Open Sci.* **2018**, *5*, 171792. [[CrossRef](#)]



4. Xiong, S.-J.; Pang, B.; Zhou, S.-J.; Li, M.-K.; Yang, S.; Wang, Y.-Y.; Shi, Q.; Wang, S.-F.; Yuan, T.-Q.; Sun, R.-C. Economically competitive biodegradable PBAT/lignin composites: Effect of lignin methylation and compatibilizer. *ACS Sustain. Chem. Eng.* **2020**, *8*, 5338–5346. [[CrossRef](#)]
5. Ferreira, F.V.; Cividanes, L.S.; Gouveia, R.F.; Lona, L.M.F. An overview on properties and applications of poly(butyleneadipate-co-terephthalate)–PBAT based composites. *Polym. Eng. Sci.* **2019**, *59*, E7–E15. [[CrossRef](#)]
6. Volanti, M.; Cespi, D.; Passarini, F.; Neri, E.; Cavani, F.; Mizsey, P.; Fozer, D. Terephthalic acid from renewable sources: Early-stage sustainability analysis of a bio-PET precursor. *Green Chem.* **2019**, *21*, 885–896. [[CrossRef](#)]
7. Skoog, E.; Shin, J.H.; Saez-Jimenez, V.; Mapelli, V.; Olsson, L. Biobased adipic acid—The challenge of developing the production host. *Biotechnol. Adv.* **2018**, *36*, 2248–2263. [[CrossRef](#)] [[PubMed](#)]
8. Silva, R.G.C.; Ferreira, T.F.; Borges, É.R. Identification of potential technologies for 1,4-Butanediol production using prospecting methodology. *J. Chem. Technol. Biotechnol.* **2020**, *95*, 3057–3070. [[CrossRef](#)]
9. Kijchavengkul, T.; Auras, R.; Rubino, M.; Ngouajio, M.; Fernandez, R.T. Assessment of aliphatic–aromatic copolyester biodegradable mulch films. Part I: Field study. *Chemosphere* **2008**, *71*, 942–953. [[PubMed](#)]
10. Jian, J.; Xiangbin, Z.; Xianbo, H. An overview on synthesis, properties and applications of poly(butylene-adipate-co-terephthalate)–PBAT. *Adv. Ind. Eng. Polym. Res.* **2020**, *3*, 19–26. [[CrossRef](#)]
11. Lawton, J.W. Zein: A history of processing and use. *Cereal Chem.* **2002**, *79*, 1–18. [[CrossRef](#)]
12. Oymaci, P.; Altinkaya, S.A. Improvement of barrier and mechanical properties of whey protein isolate based food packaging films by incorporation of zein nanoparticles as a novel bionanocomposite. *Food Hydrocolloids* **2016**, *54*, 1–9. [[CrossRef](#)]
13. Oh, J.-H.; Wang, B.; Field, P.D.; Aglan, H.A. Characteristics of edible films made from dairy proteins and zein hydrolysate cross-linked with transglutaminase. *Int. J. Food Sci. Technol.* **2004**, *39*, 287–294. [[CrossRef](#)]
14. Kadam, D.M.; Thunga, M.; Srinivasan, G.; Wang, S.; Kessler, M.R.; Grewell, D.; Yu, C.; Lamsal, B. Effect of TiO<sub>2</sub> nanoparticles on thermo-mechanical properties of cast zein protein films. *Food Packag. Shelf Life* **2017**, *13*, 35–43. [[CrossRef](#)]
15. Anaya-Esparza, L.M.; Villagrán-de la Mora, Z.; Rodríguez-Barajas, N.; Sandoval-Contreras, T.; Nuño, K.; López-de la Mora, D.A.; Pérez-Larios, A.; Montalvo-González, E. Protein–TiO<sub>2</sub>: A functional hybrid composite with diversified applications. *Coatings* **2020**, *10*, 1194. [[CrossRef](#)]
16. Guo, X.; Ren, C.; Zhang, Y.; Cui, H.; Shi, C. Stability of zein-based films and their mechanism of change during storage at different temperatures and relative humidity. *J. Food Process. Preserv.* **2020**, *44*, e14671. [[CrossRef](#)]
17. Százdí, L.; Pukánszky, B.; Vancso, G.J.; Pukánszky, B. Quantitative estimation of the reinforcing effect of layered silicates in PP nanocomposites. *Polymer* **2006**, *47*, 4638–4648. [[CrossRef](#)]
18. Pegoretti, A.; Dorigato, A.; Penati, A. Tensile mechanical response of polyethylene—Clay nanocomposites. *eXPRESS Polym. Lett.* **2007**, *1*, 123–131. [[CrossRef](#)]
19. Nanni, A.; Messori, M. Thermo-mechanical properties and creep modelling of wine lees filled Polyamide 11 (PA11) and Polybutylene succinate (PBS) bio-composites. *Compos. Sci. Technol.* **2020**, *188*, 107974. [[CrossRef](#)]
20. Dorigato, A.; D’Amato, M.; Pegoretti, A. Thermo-mechanical properties of high density polyethylene—Fumed silica nanocomposites: Effect of filler surface area and treatment. *J. Polym. Res.* **2012**, *19*, 9889. [[CrossRef](#)]
21. Kang, S.; Hong, S.I.; Choe, C.R.; Park, M.; Rim, S.; Kim, J. Preparation and characterization of epoxy composites filled with functionalized nanosilica particles obtained via sol–gel process. *Polymer* **2001**, *42*, 879–887. [[CrossRef](#)]